

IMPROVING THE OHMIC PROPERTIES OF Au/Ni–Mg/p–GaN CONTACTS BY ADDING SWCNT METALLIZATION INTERLAYER BETWEEN METAL AND p–GaN LAYERS

Jozef Liday* — Peter Vogrinčič* — Viliam Vretenár** — Ivan Hotový*
— Mário Kotlár* — Marián Marton* — Vlastimil Řeháček*

We have examined electrical properties and concentration depth profiles of contact structures Au/Ni-Mg-(O)/SWCNT/p-GaN and Au/Ni-Mg-O/p-GaN, thus with and without an interlaying layer of single-walled carbon nanotubes (SWCNT). The metallization layers were deposited on p-GaN by DC reactive magnetron sputtering in an atmosphere with and without a low concentration of oxygen (cca 0.2 at%). The contacts were annealed in N₂. We have found that the structure containing the SWCNT interlayer exhibits lower values of contact resistivity in comparison with an otherwise identical contact without the SWCNT interlayer.

Key words: p-GaN, Au/Ni-Mg-O/p-GaN, Au/Ni-Mg-(O)/SWCNT/p-GaN, single-walled carbon nanotubes (SWCNT), ohmic contact, specific contact resistance, circular transmission line method (CTLM)

1 INTRODUCTION

Gallium nitride has lately attracted significant attention for various optoelectronic applications such as light emitting diodes, laser diodes, etc. One of the factors limiting the reliability and performance of these devices is the possibility to create a low-resistance ohmic contact to p-type GaN. These contacts still present a big problem, mainly because of difficult achieving of high charge carrier concentrations ($> 10^{18} \text{cm}^{-3}$) [1]. For improving the ohmic properties of the p-GaN contact, a number of metallization layouts have been used. However, the best contact structure to p-GaN seems to be the Au/Ni structure, namely because of the relatively good values of contact resistance and in the case of very thin layers also thanks to its optical transparency. It was found that annealing of such a thin Ni/Au bilayer in air brings about a change of Ni into NiO, diffusion of Au into the interface and at the same time an improvement in the transparency of the metallization layer [2-7].

By examining the effect of a NiO_x layer with a low concentration of oxygen deposited by reactive magnetron sputtering upon the electrical properties of ohmic contacts Au/NiO_x/p-GaN [8] it was found that a low-resistance ohmic contact was provided by annealing not only in oxygen but also in nitrogen. Both annealing modes lead to reconstruction of the contact into a metal/p-NiO/p-GaN structure. The ohmic nature of these contacts is predetermined by formation of a thin oxide layer (NiO) at the metal/p-GaN interface. Promising results were reached by incorporating group II dopants into the metallization layer intended to increase the charge carrier concentration in the surface region of p-GaN [9, 10]. Contact structures Au/Ni-Mg-O/p-GaN and Au/Ni-Zn-O/p-

GaN exhibited lower values of specific contact resistance than the same structures without Mg and Zn dopants [11].

In [12], low-resistance ohmic contacts to p-GaN were presented based on a layer of single-walled carbon nanotubes. Thanks to its specific properties, this material is highly promising for creating ohmic contacts to p-GaN. It has both semiconducting and metallic properties, whereas the semiconductor exhibits p-type conductivity, and unlike metallic layers it also has excellent thermal and optical properties [13, 14].

The objective of this work is to improve the ohmic properties of the contact to p-type GaN by modifying the original Au/Ni/p-GaN structure to a Au/Ni-Mg-(O)/SWCNT/p-GaN structure. Between the Ni layer containing Mg p-dopant deposited by reactive magnetron sputtering at low concentration of oxygen (approx. 0.2 at%) and the layer of p-GaN a layer of single-walled carbon nanotubes (SWCNT) was deposited by spraying a solution of carbon nanotubes (CNT) with optimized density and homogeneity. The specific contact resistance was determined by the circular transmission line method (CTLM). The effects of the contact structure annealing temperature and time were investigated.

2 EXPERIMENTAL

Metalorganic vapour phase epitaxy (MOVPE) p-GaN layers with a thickness of 800 nm, carrier concentration $2 \times 10^{17} \text{cm}^{-3}$ and mobility around $5 \text{cm}^2/\text{Vs}$ produced in the Magnetic Spin Materials Group at Johannes Kepler University in Linz were used for preparation of Au/Ni-Mg-(O)/SWCNT/p-GaN structures. The p-GaN layers

* Institute of Electronics and Photonics, Slovak University of Technology, Ilkovičova 3, 812 19 Bratislava, Slovakia, jozef.liday@stuba.sk;

** Danubia NanoTech, s.r.o., Ilkovičova 3, 841 04 Bratislava, Slovakia

were first sequentially ultrasonically treated for 5 minutes in each step in acetone, isopropanol, DI water, dried with compressed N_2 and then chemically etched in $HCl:H_2O$ (1:1) etchant to remove the surface native oxide. On such p-GaN layers, SWCNTs prepared by the standard laser ablation method followed by a purification process were deposited. High-quality SWCNTs prepared in this way were deposited on p-GaN by spray coating using an off-the-shelf airbrush. As a solution, 2mg of SWCNTs diluted with 20 ml of N-methyl-2-pyrrolidone were tip-sonicated for 10 min. In order to accelerate the evaporation of the solvent and prevent formation of bigger droplets the substrate was heated to $165^\circ C$. The thickness of the SWCNT layer was approx. 75 nm. This thickness guarantees a sufficient (more than 60%) optical transmittance of the SWCNT layer [12].

After processing in $HCl:H_2O$ (1:1) etchant, patterns were created on the SWCNT layer by lift-off technique needed for measuring the specific contact resistance by the circular transmission line method. In the end, the metal thin films were deposited by DC magnetron sputtering. The $Ni_{92}Mg_8$ (10 nm) thin film was prepared by DC reactive magnetron sputtering from a Ni target containing 8 at% of Mg in an atmosphere of argon with and without a low concentration of oxygen (approx 0.2 at%). The upper Au layer (50 nm) was also prepared by DC magnetron sputtering. The distance between the target and the substrate was approximately 75 mm. A sputtering power of 600 W was used. Both the argon inert flow and oxygen reactive flow were controlled by mass flow controllers. The total gas pressure was kept at 0.5 Pa.

After rinsing out the photoresist from the patterns for CTLM measurement, the SWCNT layer was denuded by etching in RF oxygen plasma using Plasma Etch PE-200 equipment.

After deposition the samples were subsequently annealed in N_2 in a rapid thermal annealing furnace at a temperature of $700^\circ C$ for 1 minute. $I-V$ measurements were performed on a Keithley 2400 SourceMeter equipped with MDC micropositioners by applying a voltage ramp from 10 V to +10 V and measuring the respective current. From the slope of the $I-V$ curves, the total resistance was determined. The specific contact resistance was determined using the model of Marlow and Das.

To study the effects of the annealing temperature and time upon the specific contact resistance of Au/Ni-Mg(-O)/SWCNT/p-GaN contact, identically prepared samples were annealed, immediately after deposition, in a rapid thermal annealing furnace at temperatures from $400^\circ C$ to $800^\circ C$ for 1 to 3 minutes.

3 RESULTS

Figure 1 shows the contact structure Au/Ni-Mg/SWCNT/p-GaN for ohmic contact characterization by the circular transmission line method. The outer radius of the test patterns is $155\ \mu m$ with gap length from 5 to 45

μm . Measurements of the influence of the annealing temperature and time upon the specific contact resistance of Au/Ni-Mg (-O)/SWCNT/p-GaN and Au/Ni-Mg-O/ p-GaN contacts on identically prepared samples revealed that the lowest value of specific contact resistance of the contacts both with and without the SWCNT was achieved after annealing in N_2 , in the former case at $700^\circ C$ for 1 minute, in the latter case at $500^\circ C$ for 2 minutes and these parameters were further used in the presented study.

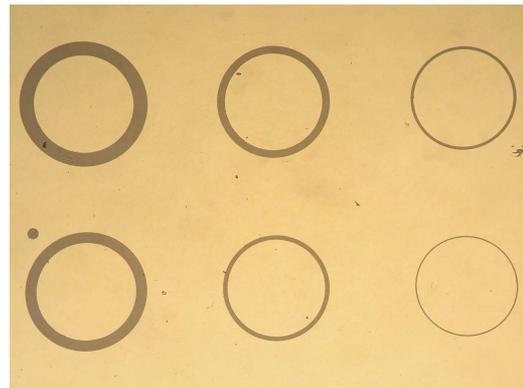


Fig. 1. Au/Ni-Mg /SWCNT/p-GaN contact structure for CTLM ohmic contact characterization. The outer radius of the test patterns is $155\ \mu m$ with gap length from 5 to $45\ \mu m$.

Measurements of the specific contact resistance Au/Ni-Mg(-O)/SWCNT/p-GaN contacts by CTLM have shown that even annealing in N_2 at $400^\circ C$ for 1 minute resulted in ohmic properties of contacts. Figure 2 displays the $I-V$ curves for gap length 5, 10 and $25\ \mu m$ from CTLM measurements of Au/Ni-Mg (-O)/SWCNT/p-GaN contacts annealed in N_2 at $700^\circ C$ for 1 minute and of Au/Ni-Mg-O/p-GaN contacts annealed in N_2 at $500^\circ C$ for 2 minutes. These results clearly demonstrate that ohmic contacts with the SWCNT intermediate layer exhibit better ohmic properties. The obtained results of the specific contact resistances are summarized in Table 1.

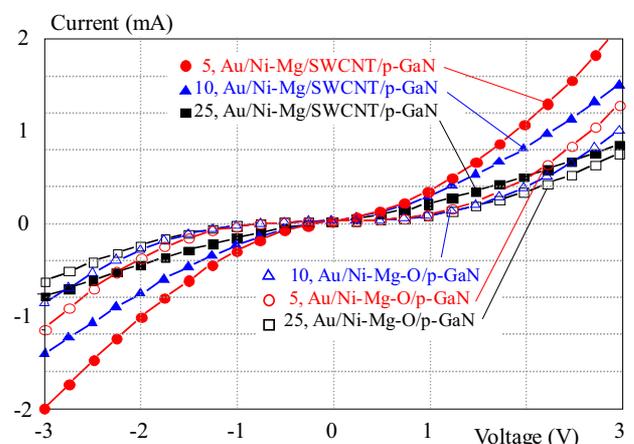


Fig. 2. $I-V$ curves for gap length 5, 10 and $25\ \mu m$ from CTLM measurements of Au/Ni-Mg/SWCNT/p-GaN contacts annealed in N_2 at $700^\circ C$ for 1 minute and of Au/Ni-Mg-O/p-GaN contacts annealed in N_2 at $500^\circ C$ for 2 minutes

Table 1. Specific contact resistances of annealed Au/Ni-Mg(-O)/SWCNT/p-GaN contacts (in N₂ at 400 °C and 700 °C for 1 minute) and Au/Ni-Mg-O/p-GaN contact (in N₂ at 500 °C for 2 minutes)

contact structure annealed in N ₂	specific contact resistance (Ωcm ²)		
	400 °C, 1min	500 °C, 2min	700 °C, 1min
Au/Ni-Mg/SWCNT/p-GaN	2.8 × 10 ⁻³		7.3 × 10 ⁻⁴
Au/Ni-Mg-O/SWCNT/p-GaN	4.3 × 10 ⁻²		3.0 × 10 ⁻³
Au/Ni-Mg-O/p-GaN		7.5 × 10 ⁻³	

In the study of the Au/Ni-O/p-GaN structure [8] it was found that RTA annealing in nitrogen or in a mixture of oxygen and nitrogen caused reconstruction of the system into a metal/p-NiO/p-GaN sequence and that its ohmic properties were predetermined by creating a thin NiO oxide layer on the metal/p-GaN interface. In [11] it was reported that by adding p-type dopants (Mg or Zn) into the Ni-O layer brought about an increase in the density of free charge carriers in the sub-surface region of p-GaN resulting in lower values of contact resistivity in comparison with otherwise identical contacts without dopants. In our opinion the further improvement of the ohmic properties of the Au/Ni-Mg-O/p-GaN contact by adding the SWCNT interlayer between the metal Au/Ni-Mg(-O) and p-GaN layers is related to the existence of a contact scheme metal/p-SWCT/p-GaN.

4 CONCLUSION

With intention to improve the ohmic properties of the Au/Ni-Mg-O/p-GaN contact to p-type GaN we have studied a modified contact structure Au/Ni-Mg(-O)/SWCNT/p-GaN in which a layer of SWCNT was deposited between the Ni layer containing Mg p-dopant and the layer of p-GaN. It has been found that the contact created by a layer of carbon nanotubes deposited on p-GaN by spray coating and covered by Ni-Mg and Au deposited by reactive magnetron sputtering in an atmosphere with and without a low concentration of oxygen (approx. 0.2 at%) provides a lower resistivity ohmic contact in comparison with an identical contact structure without the SWCNT interlayer. It is believed that the ohmic nature is related to the existence of a contact scheme metal/p-SWCT/p-GaN.

Acknowledgements

The work was supported by the Scientific Grant Agency of the Ministry of Education of the Slovak Republic and of the Slovak Academy of Sciences (project VEGA No. 1/1197/12).

REFERENCES

- [1] MURAKAMI, M. *et al* : Ohmic contacts for compound semiconductors, *Crit. Rev.in Solid State and Mater. Sci.* **23** No. 1 (1998).
- [2] HO, J. K. *et al* : Low-resistance ohmic contacts to p-type GaN achieved by the oxidation of Ni/Au films, *J. Appl. Phys.* **86** (1999), 4491.
- [3] MISTELE, D. *et al* : Ohmic contacts for compound semiconductors, *J. Cryst. Growth* No. 230 (2001), 564.
- [4] JANG, H. W. *et al* : Mechanism for ohmic contact formation of oxidized Ni/Au on p-type GaN, *J. Appl. Phys.* **97** (2003), 1748.
- [5] WENZEL, R. *et al* : Ohmic contacts on p-GaN, *Mater. Sci. Semicond. Process.* **4** (2001), 357.
- [6] PARK, M. R. *et al* : Microstructure and electrical properties of low temperature processed ohmic contacts to p-type GaN, *ETRI Journ.* **24** (2002), 349.
- [7] WANG, S. H. *et al* : Environmental and thermal aging of Au/Ni/p-GaN ohmic contacts annealed in air, *J. Appl. Phys.* **91** (2002), 3711.
- [8] LIDAY, J. *et al* : Investigation of NiOx-based contacts on p-GaN, *J. Mater. Sci: Mater. Electron.* **19** (2008), 855.
- [9] SONG, J. O. *et al* : Formation of low resistance and transparent ohmic contacts to p-type GaN using Ni-Mg solid solution, *Appl. Phys. Lett.* **83** (2004), 3513.
- [10] SONG, J. O. *et al* : Low-resistance and transparent ohmic contacts to p-type GaN using Ni-Zn solid solution /Au scheme, *Appl. Phys. Lett.* **84** (2004), 4663.
- [11] LIDAY, J. *et al* : Improving the Ohmic properties of contacts to p-GaN by adding p-type dopants into the metallization layer, *J. Electrical Engin.* **63** (2012), 397.
- [12] LEE, K. *et al* : Single wall carbon nanotubes for p-type ohmic contacts to p-GaN light-emitting diodes, *Nano Lett.* **4** (2004), 911.
- [13] POPOV, V. N. : Carbon nanotubes: properties and application, *Mater. Sci. Engin.* **R43** (2004), 61.
- [14] ZHAO, J. *et al* : Optical properties and photonic devices of doped carbon nanotubes, *Analytica Chim. Acta.* **568** (2006), 161.

Received 7 February 2013

Jozef Liday, (Assoc Prof, PhD), **Peter Vogrinčič** (Ing), **Viliam Vretenár** (Ing, PhD) – for biographies see NO. 5 of this Journal volume.

Ivan Hotový (Prof, DrSc) received his MSc in Electronics from the Slovak University of Technology in Bratislava in 1982 and his PhD in Electronics from the Slovak University of Technology in 1994. He is a scientific worker and lecturer at Department of Microelectronics, FEIT STU. His current research interests include the development of gas sensors, magnetron sputtering of metal oxide films and plasma etching of compound semiconductors.

Mário Kotlár (Ing), **Marián Marton** (Ing, PhD), **Vlastimil Řeháček** – for biographies see NO. 5 of this Journal volume.